


28-150 – Product data sheet

Presentation:

The 28-150 is IFB classical insulating brick for 1500°C temperature applications. With high alumina content (>58%) and low iron oxide (<1.05%) it offers high insulation (0.39 W/m.K at 1200°C) and good mechanical properties (CCS >2.2 MPA).

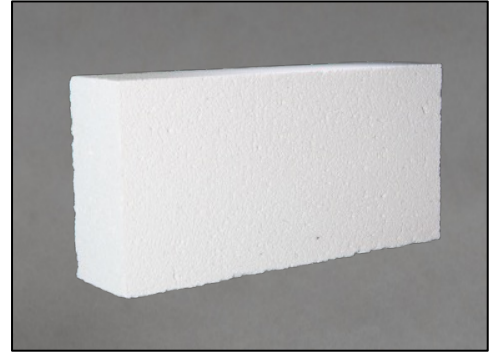

Maximum classified temperature: **1500°**.



French refractory clays & local organic filler.

Properties :	Standards	Units	Average μ	Limits	
				Tl (low)	Th (high)
Classification	ISO 2245		150L		
	ASTM C155		28		
Bulk density	EN 1094-4	g/cm ³	0,87		0,96
Cold Crushing Strength (// to extrusion)	ISO 8895	Mpa	3,5	2,2	
Permanent Linear Change (12h at 1500°C)	ISO 2477	%	-0,7	-1	
Chemical Analysis :	ISO 12677	%			
(XRF)	Al ₂ O ₃		61	58	
	SiO ₂		35		
	Fe ₂ O ₃		0,8		1,05
	TiO ₂		0,3		
	CaO+MgO		0,4		
	Na ₂ O+K ₂ O		1,5		1,7
Thermal Conductivity :	ASTM C182	W/m.K			
(through 114mm dimension)	200°C		0,32		
	400°C		0,33		
	600°C		0,35		
	800°C		0,37		
	1000°C		0,38		
	1200°C		0,39		
Reversible Thermal Expansion : (20°C to 1000°C)	ISO 16835	%	0,5		
Pyroscopic Cone Equivalent :	ISO 528	°C	1730		

Dimensional tolerances:	Standard Pieces	Non-Standard Pieces
	Length	±1.5mm
Width	±1.5mm	
Thickness	±1.5mm	
Squaring	1mm / 100mm	

Other Information :	C 1500 S or H	RL 75 S or H
Recommended mortar	C : Heat set S : Dry / Powder	RL : Air set H : Ready to Use

Ref. 2023/02

Physical properties are based on averages of routine quality controls carried out on standard bricks. Averages and standard deviations are indicative values, limits (Tl and Th) are guaranteed values.



IFB Refractories bricks are 100% made in France, from local raw materials, with a special attention to the environment.

Website: www.ifbgroup.fr
Email: ifb-sales@ifbgroup.fr